

Effective trapping time of electrons and holes in different silicon materials irradiated with neutrons, protons and pions

G. Kramberger¹, V. Cindro, I. Mandić, M. Mikuž, M. Zavrtnik

*Jožef Stefan Institute and Department of Physics,
University of Ljubljana, SI-1000 Ljubljana, Slovenia*

Abstract

Silicon diodes fabricated on oxygenated and non-oxygenated silicon wafers with different bulk resistivities (1, 2 and 15 k Ω cm) were irradiated with neutrons, pions and protons to fluences up to 2.4×10^{14} n/cm⁻². Effective trapping times for electrons and holes were determined by the charge correction method in the temperature range between -50°C and 20°C. The measured effective trapping probabilities scale linearly with fluence and decrease with increasing temperature. Irradiation with charged hadrons resulted in about 30 % higher trapping probabilities than with neutrons at the same equivalent fluence. No dependence on silicon resistivity and oxygen concentration was found. The temperature dependence could be parameterized by a power-law scaling. Accelerated annealing at 60°C showed a 30% increase of hole trapping, measured at 10°C, and a decrease by about the same amount for electron trapping, both at a time scale of 10 hours.

PACS: 85.30.De; 29.40.Wk; 29.40.Gx

Key words: Effective carrier trapping time, Silicon detectors, Charge collection efficiency,

1 Introduction

Segmented silicon detectors will be widely used in experiments at the Large Hadron Collider (LHC) for tracking of charged particles. The high luminosity

¹ Corresponding author; Address: Jožef Stefan Institute, Jamova 39, SI-1000 Ljubljana, Slovenia. Tel: (+386) 1 4773512, fax: (+386) 1 4257074, e-mail: Gregor.Kramberger@ijs.si

and the large proton-proton inelastic cross section will result in intense fluxes of heavy particles, mainly pions and neutrons, to which silicon detectors and accompanying read-out electronics will be exposed. As an example, the ATLAS Semiconductor Tracker will accumulate fluences up to about $2 \times 10^{14} \text{ cm}^{-2}$ 1 MeV neutron non-ionizing energy loss (NIEL) equivalent during its ten year operation at the collider [1].

Trapping of the drifting charge in traps having emission times longer than the shaping time of the electronics ($\sim 25 \text{ ns}$) will reduce the signal [2]. This could be partly overcome by over-depleting of the detector, thereby reducing the drift time and probability for trapping. However the increased effective dopant concentration and leakage current after irradiation impose practical limitations to applicable voltages due to detector breakdown and thermal runaway.

Defect dynamics and the related change of effective dopant concentration and leakage current with time have been extensively studied - see for example [3]. Data on trapping times are, however, relatively scarce [4,5]. The knowledge of the effective trapping time is, however, of vital importance for an accurate prediction of detector performance at the LHC.

In this work we present a systematic measurement of electron and hole trapping times after irradiation of silicon diodes with neutrons, pions and protons to fluences up to $2.4 \times 10^{14} \text{ cm}^{-2}$ 1 MeV neutron NIEL equivalent. The method used for determination of the effective trapping time is based on the correction of time-resolved current pulse shapes due to trapping, recently proposed independently by two groups [6,7]. The diodes used in this study were fabricated on silicon of various resistivities and oxygen concentrations. The effective trapping times were determined in the temperature range between -50°C and 20°C . Evolution of trapping with time after irradiation was also investigated.

2 The Measurement Set-up

A transient current technique (TCT) set-up was used to measure the current response of the detectors to short light pulses. Diodes were mounted in a temperature-controlled optical liquid-nitrogen cryostat, allowing light injection from both p^+ and n^+ sides of the diode. Current signals were amplified with a fast current amplifier and transmitted to a 500 MHz oscilloscope. A red laser with a wavelength of 670 nm (absorption depth $3.3 \mu\text{m}$ at 20°C) and pulse width of approximately 1 ns was used. The short penetration depth of the red light gives the possibility to inject electrons by p^+ side illumination and holes by n^+ side illumination.

The charge correction method for the determination of the effective trapping

time is based on the assumption that the decrease of charge due to trapping is exponential with time, as the charge drifts through the detector. Therefore the integral of the induced current (induced charge) does not saturate in an irradiated detector but exhibits a rise also at voltages above the full depletion voltage (V_{FD}). At higher voltages the drift time is reduced due to the higher electric field and thus less charge gets trapped. To determine the effective trapping time (τ_{eff}), the measured induced currents ($I_m(t)$) are corrected with an exponential $\exp(t/\tau_{eff})$ so that the integral of the corrected current gives equal charges for all voltages above V_{FD} .

For a detailed explanation of the set-up and of the charge correction method the reader is referred to [6].

2.1 Irradiations

Neutron irradiations took place in the core of the TRIGA nuclear reactor of the Jožef Stefan Institute in Ljubljana. The measured and simulated spectrum of neutrons with energies ranging from thermal to fast (~ 10 MeV) can be found in [8]. Fast neutron ($E > 0.1$ MeV) fluxes up to 4×10^{12} cm^{-2} s^{-1} were measured by gold activation [9] and scaled with the calculated damage factor. They agree with the values obtained from the leakage current method [10] to better than 10% [11]. During the irradiation the diodes were kept at a temperature around 20°C. The longest irradiation time was about 5 minutes.

Irradiations with pions were performed at the Paul Scherrer Institute in Villigen, Switzerland. The energy of pions was 200 MeV. Equivalent fluences were determined from aluminium foil activation using the damage factor 1.2 (average of values reported in [12] and [13]) as well as with the leakage current method. The highest fluence of 2.4×10^{14} cm^{-2} was reached within a day. The temperature during irradiation was around 25°C.

24 GeV/c protons from the CERN PS were used for proton irradiations. Fluences were determined with the same methods as for pion irradiations. The damage factor used for PS protons is 0.62 [3].

2.2 Samples

Several $p^+ - n - n^+$ pad detectors processed on high (15 $\text{k}\Omega\text{cm}$) and low resistivity (1 $\text{k}\Omega\text{cm}$, 2 $\text{k}\Omega\text{cm}$) standard and oxygen enriched silicon wafers were irradiated. The samples were produced at ST Microelectronics and at Brookhaven National Laboratory (BNL). Their properties and treatment is listed in Table 1. A hole ($\phi = 2$ mm) in the metalization on the p^+ side of the

diode was used for light injection, while on the n^+ side a mesh metalization was provided for the same purpose.

During and after irradiation the diodes were kept unbiased. After the irradiation they were mounted onto an aluminium support using a room-temperature curing conductive glue. Then they were annealed at $T = 20^\circ\text{C}$ to the minimum in V_{FD} . The evolution of V_{FD} during annealing was measured with the $C - V$ method at the frequency $\nu = 10$ kHz. The minimum values of V_{FD} are shown in Fig. 1. There is a nearly perfect agreement of V_{FD} for samples fabricated on non-oxygenated high-resistivity material at equal NIEL equivalent fluences for different particles. Taking into account the negligible remaining donor concentration after irradiation this confirms the dosimetry measurements at different irradiation sites. Once reaching the minimum in V_{FD} the diodes were stored at $T = -17^\circ\text{C}$ until the measurements of effective trapping times were performed.

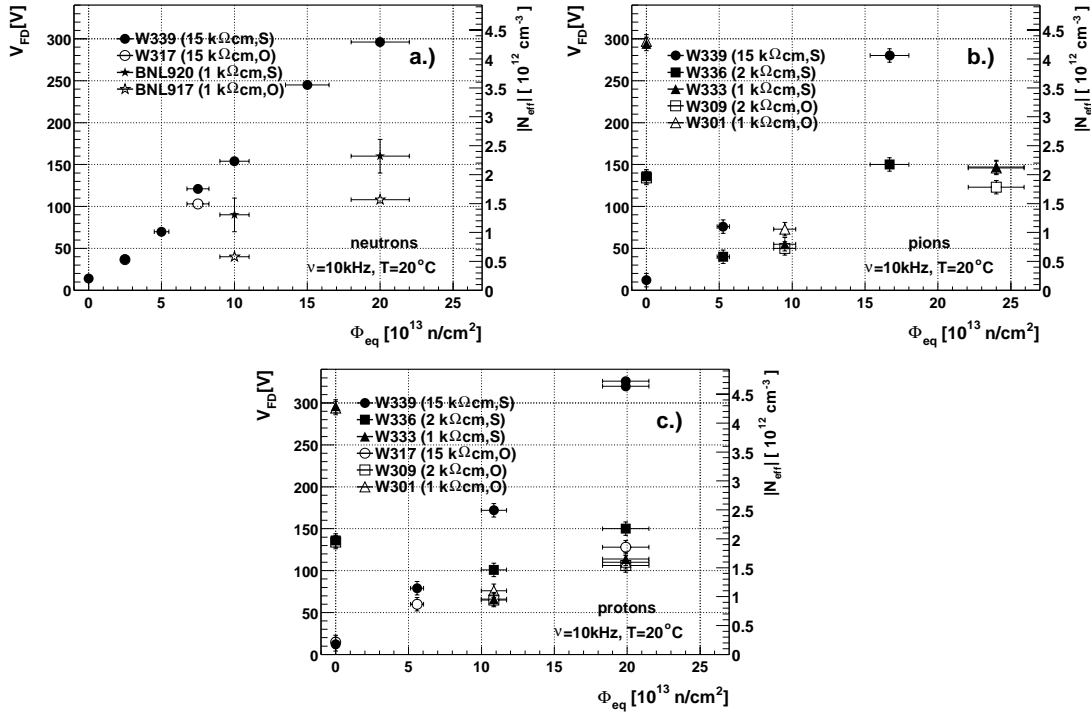


Fig. 1. V_{FD} as measured with the $C - V$ method at the annealing minimum: a.) neutron, b.) pion and c.) proton irradiation. V_{FD} of the BNL920 samples has a larger uncertainty due to non-ideal $C - V$ characteristics. The material type is given in brackets: O for oxygenated and S for standard material.

3 Results

If the thermal velocity v_{th} is large compared to the drift velocity (which applies to our case), the distance l traversed by the drifting charge q , and thus the

Table 1

Irradiation fluences and diode properties. The samples labeled with W were processed by ST Microelectronics on Wacker silicon wafers, while those labeled with BNL were processed on Topsil silicon. Time and temperature of diffusion oxygenation is given. The silicon crystals were cut along the $\langle 111 \rangle$ plane.

Sample	Oxygenation	Initial resistivity and V_{FD}	Fluences Φ_{eq} [10^{13} n/cm ²]
W339	no	15 k Ω cm $V_{FD} = 10-15$ V	neutrons: 0, 2.5, 5, 7.5, 10, 15, 20 pions: 5.3, 16.7 protons: 5.6 , 10.9 , 19.9
W336	no	2 k Ω cm $V_{FD} \approx 135$ V	neutrons: - pions: 5.3, 16.7 protons: 10.9 , 19.9
W333	no	1 k Ω cm $V_{FD} \approx 295$ V	neutrons: - pions: 9.5, 24 protons: 10.9 , 19.9
W317	60 h at $T = 1200^\circ$ C	15 k Ω cm $V_{FD} \approx 20$ V	neutrons: 2.5, 7.5 pions: - protons: 5.6, 19.9
W309	60 h at $T = 1200^\circ$ C	2 k Ω cm $V_{FD} \approx 135$ V	neutrons: - pions: 9.5, 24 protons: 10.9 , 19.9
W301	60 h at $T = 1200^\circ$ C	1 k Ω cm $V_{FD} \approx 295$ V	neutrons: - pions: 9.5, 24 protons: 10.9
BNL920	no	≈ 1 k Ω cm $V_{FD} = 170-210$ V	neutrons: 10, 20 pions: - protons: -
BNL917	12 h at $T = 1200^\circ$ C	≈ 1 k Ω cm $V_{FD} \approx 250$ V	neutrons: 10, 20 pions: - protons: -

number of collisions, is proportional to the drift time ($l = v_{th} \cdot t$), allowing to introduce the effective trapping probability by

$$q(t) = q(t=0) \cdot e^{-\frac{t}{\tau_{eff}}}. \quad (1)$$

Here $q(t)$ represents the drifting charge, electrons or holes, created at $t = 0$. The trapping probability can be expressed as:

$$\frac{1}{\tau_{eff_{e,h}}} = \sum_t N_t (1 - P_t^{e,h}) \sigma_{t_{e,h}} v_{th_{e,h}}. \quad (2)$$

Here N_t denotes the trap concentration, $P_t^{e,h}$ its occupation probability with the relevant carrier, $v_{th_{e,h}}$ the thermal velocity of drifting carriers and the $\sigma_{t_{e,h}}$ the carrier capture cross-section. The sum runs over all traps. For traps introduced directly by irradiation, N_t has the form

$$N_t = g_t \cdot \Phi_{eq} \cdot f_t(t) \quad (3)$$

with g_t the introduction rate and $f_t(t)$ representing (exponential) trap annealing with time after irradiation. On the other hand, Eq. 3 with appropriately modified $f_t(t)$ can also describe traps originating from decays of primary defects. A more general form, including Φ_{eq}^2 terms, would be needed to describe traps formed by reactions between defects.

If traps described by Eq. 3 ($N_t \propto \Phi_{eq}$) dominate, the effective trapping probability at a given temperature and time after irradiation can be parameterized as

$$\frac{1}{\tau_{eff_{e,h}}} = \beta_{e,h}(t, T) \Phi_{eq}. \quad (4)$$

The aim of this study is to evaluate $\beta_{e,h}$ as a function of irradiation particle type, silicon material and temperature, and its dependence on time after irradiation.

3.1 Material and particle dependence

The effective trapping probability for electrons and holes, measured at $T = -10^\circ\text{C}$ after ~ 10 days of room temperature annealing, for different particles and silicon materials can be seen in Fig. 2. A clear linear dependence of the trapping probability on Φ_{eq} can be observed, indicating an effective absence

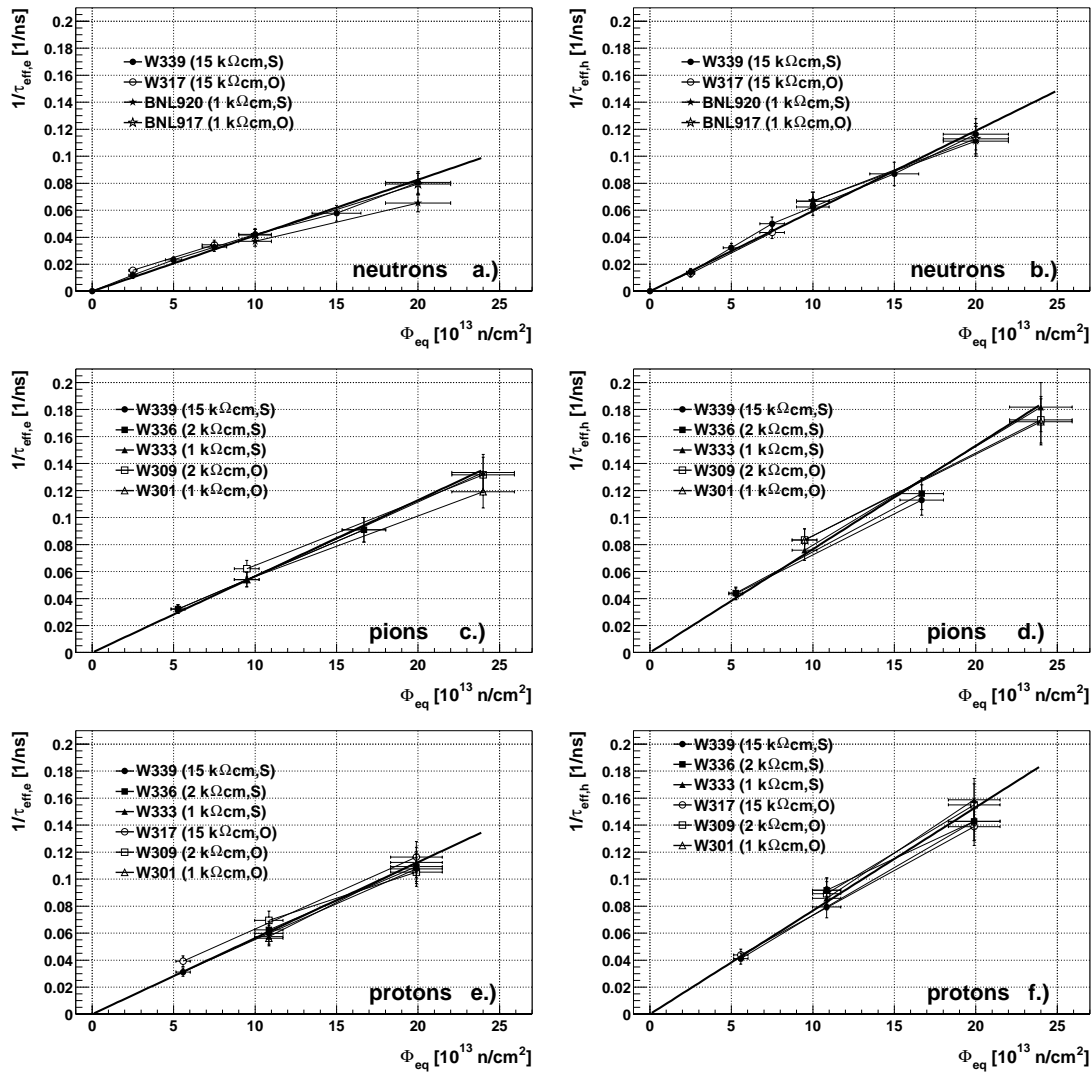


Fig. 2. Fluence dependence of effective trapping probability for electrons and holes for neutron, pion and proton-irradiated samples : a.) electrons (neutron irradiation), b.) holes (neutron irradiation), c.) electrons (pion irradiation) and d.) holes (pion irradiation) e.) electrons (proton irradiation) and f.) holes (proton irradiation). Measurements were taken at $T = -10^\circ\text{C}$ after ~ 10 days of annealing at room temperature. Resistivity and material type are given in brackets: O-oxygenated and S-standard material.

of trapping centres formed in second-order reactions. The resistivity of the silicon material in the range from 1 k Ωcm to 15 k Ωcm does not influence the effective trapping probability. There is also no difference between standard and oxygenated silicon materials, although the latter exhibits a smaller increase of negative space charge upon charged hadron irradiation [3].

It appears, however, that different particle types have different $\beta_{e,h}$ as can be seen in Table 2. $\beta_{e,h}$ for charged hadrons are about 30-40% larger than those for neutrons. The effective trapping probability thus does not scale with

NIEL when comparing neutrons with charged particles. As demonstrated in section 2.1., the agreement of V_{FD} of standard material at the same equivalent fluences for different irradiations excludes a dosimetry error required to cause the observed level of $\beta_{e,h}$ dependence on particle type. A possible qualitative explanation could be that NIEL from charged hadrons produces more point defects than NIEL of neutrons which in turn creates more cluster defects. Point defects thus appear to be more efficient as trapping centres. Since oxygen acts as a vacancy sink and is observed not to influence trapping, these defects are likely to be interstitial-related.

Table 2

β for electrons and holes for different particle types at $T = -10^\circ\text{C}$ after ~ 10 days of room temperature annealing. The error quoted does not include a $\sim 10\%$ systematic error on dosimetry.

	β_e [10^{-16} cm ² /ns]	β_h [10^{-16} cm ² /ns]
neutrons	4.1 ± 0.1	6.0 ± 0.2
pions	5.7 ± 0.2	7.7 ± 0.2
protons	5.6 ± 0.2	7.7 ± 0.2

3.2 Temperature dependence

Three parameters in $\beta_{e,h}$ depend on temperature: thermal velocity of the carriers, capture cross-sections and occupation probabilities of the traps. A square-root temperature dependence is characteristic for $v_{th_{e,h}}$. The capture cross-section dependence on temperature is poorly known, scaling as $\sigma(T)/\sigma(T_o) = (T/T_o)^m$ with m ranging between -2 and 2 is suggested in [14,15].

Let us assume that one defect dominates trapping of the drifting electrons and equivalently, there exists a dominating hole trap. The occupation probability of a trap, described by the energy level E_t , in the depleted region can be calculated using Shockley-Read-Hall statistics as [16]:

$$P_t^e(T) = \frac{1}{\frac{c_e}{c_h} \chi_t^2 + 1} \quad , \quad P_t^h(T) = 1 - P_t^e(T) \quad , \quad p \approx n \approx 0 \quad (5)$$

$$\chi_t = \exp\left(\frac{E_t - E_i}{k_B T}\right) \quad , \quad c_{e,h} = \sigma_{t_{e,h}} v_{th_{e,h}} \quad (6)$$

$$E_i = \frac{E_g}{2} + \frac{1}{2} k_b T \ln\left(\frac{P_v}{N_c}\right) \quad , \quad \frac{P_v}{N_c} = 0.371 \quad , \quad E_g = 1.12 \text{ eV} \quad (7)$$

where E_i denotes the Fermi level in intrinsic silicon, k_B the Boltzmann constant, and P_v and N_c the effective densities of states in the valence and con-

duction band, respectively.

Temperature scaling of $\beta_{e,h}$ dominated by a single trap can thus be written as:

$$\beta_{e,h}(T) = \frac{1}{\tau_{eff,e,h} \Phi_{eq}} = \beta_{e,h}(T_0) \frac{1 - P_t^{e,h}(T)}{1 - P_t^{e,h}(T_0)} \left(\frac{T}{T_0} \right)^{-m + \frac{1}{2}} \quad (8)$$

In order to study the dependence of effective trapping probability on temperature, measurements for all the diodes from Table 1 were performed in the temperature interval from 223 K to 293 K. The temperature range was constrained by practical limitations. For lower temperatures, fast drift, especially of electrons, rendered the experimental determination of τ_{eff} questionable. And at higher temperatures, the resulting reverse current was too high to be properly handled by our experimental set-up.

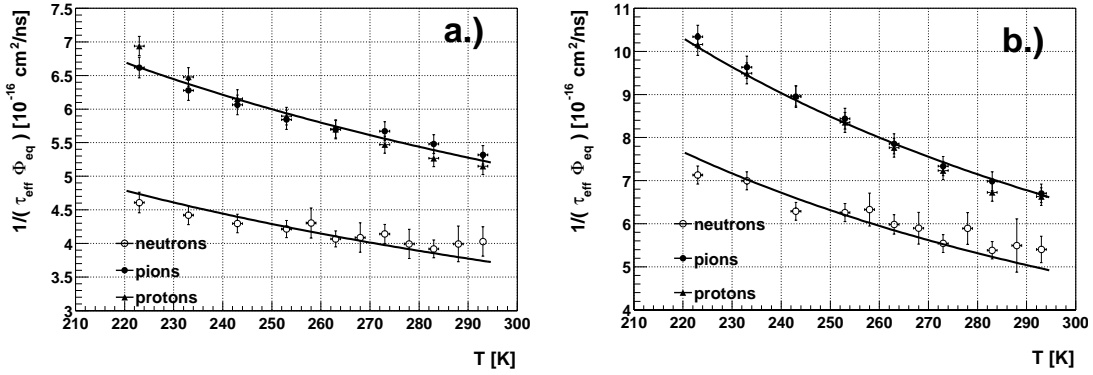


Fig. 3. Temperature dependence of β for: a.) electrons and b.) holes. The measured points are the average of β 's for all measured samples.

The measured temperature dependence of average $\beta_{e,h}$ for all three particle types is shown in Fig. 3 exhibiting a 20 - 30 % decrease of trapping probability over the temperature range covered. An examination of terms in Eq. 8 showed that such behavior could be caused either by a negative m in cross-section scaling, or by a near to mid-gap position of the trap, supported by an appropriately large c_e/c_h ratio, or a combination of the two effects. Therefore, an extraction of separate trap parameters was considered unjustified. An effective parameterization of the form

$$\beta_{e,h}(T) = \beta_{e,h}(T_0) \cdot \left(\frac{T}{T_0} \right)^{\kappa_{e,h}} \quad (9)$$

with $\kappa_{e,h}$ universal for all particle types yielded acceptable fits (see Fig. 3) to all data. Fit results are listed in Table 3. This could indicate, that the same two traps, albeit introduced at different rates, play the dominant role in trapping induced by neutron and charged hadron irradiation.

Table 3

Parameters $\kappa_{e,h}$, determining temperature scaling of $\beta_{e,h}$, as obtained from the fit of Eq. 9 to measured data.

$\kappa_e = -0.86 \pm 0.06$	$\kappa_h = -1.52 \pm 0.07$
-----------------------------	-----------------------------

3.3 Annealing of effective trapping probability

With time, defects can either decay or interact with others to form new ones. The consequence of this is a change in effective trapping probability, covered by the annealing function $f_t(t)$ in Eq. 3. Annealing of $\beta_{e,h}$ was studied with two diodes from wafers W339 (standard, 15 k Ω cm) and W317 (oxygenated, 15 k Ω cm) irradiated with neutrons to 7.5 10¹³ cm⁻². After the diodes reached the minimum in V_{FD} at room temperature, accelerated annealing was performed in steps at 60°C. Between annealing steps TCT measurements were done at $T = 10^\circ\text{C}$. The diodes were mounted to the same Peltier temperature regulator to ensure equal temperature history. Dependence of $\beta_{e,h}$ on annealing time

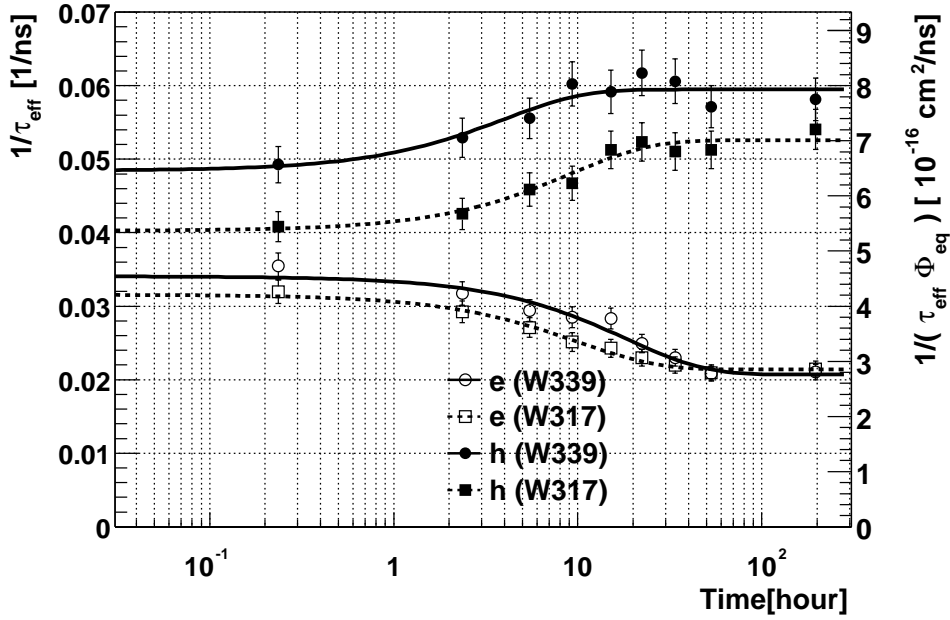


Fig. 4. Annealing of effective trapping probability at 60°C. Measurements were taken at $T = 10^\circ\text{C}$.

is shown in Fig. 4. It can be seen that, for both standard and oxygenated material, β_e at 10°C decreases with time after irradiation by about 35%, while β_h increases by about 30%. An elementary model assuming the decay of the dominant electron and hole trap into another stable one was evaluated and observed to describe the annealing data well. The relevant fit function was

$$\beta_{e,h}(t) = \beta_{0_{e,h}} \cdot e^{-\frac{t}{\tau_{e,h}}} + \beta_{\infty_{e,h}} \cdot (1 - e^{-\frac{t}{\tau_{e,h}}}) \quad (10)$$

with $\beta_{0_{e,h}} \equiv \beta_{e,h}$ and $\beta_{\infty_{e,h}}$ the trapping rates at early and late annealing times, respectively.

Table 4

Amplitudes and time constants for the parameterization of β annealing.

	β_{0_e} [$10^{-16} \frac{\text{cm}^2}{\text{ns}}$]	β_{∞_e} [$10^{-16} \frac{\text{cm}^2}{\text{ns}}$]	β_{0_h} [$10^{-16} \frac{\text{cm}^2}{\text{ns}}$]	β_{∞_h} [$10^{-16} \frac{\text{cm}^2}{\text{ns}}$]	τ_e [hour]	τ_h [hour]
W339	4.5 ± 0.2	2.8 ± 0.1	6.5 ± 0.3	7.9 ± 0.2	19 ± 5	4.2 ± 2.3
W317	4.2 ± 0.2	2.8 ± 0.1	5.4 ± 0.3	7.0 ± 0.2	10.6 ± 3.5	9.7 ± 4.5

The results of the fits are gathered in Table 4. Parameters for standard and oxygenated samples exhibit the same behavior within the rather large uncertainties. Annealing times are of order of 10 hours at 60°C, about the same order of magnitude as characteristic times of reverse annealing. Although depending in detail on the activation energy, the effect of trapping probability annealing can thus be expected to play a rather marginal role in the lifetime of a typical LHC experiment.

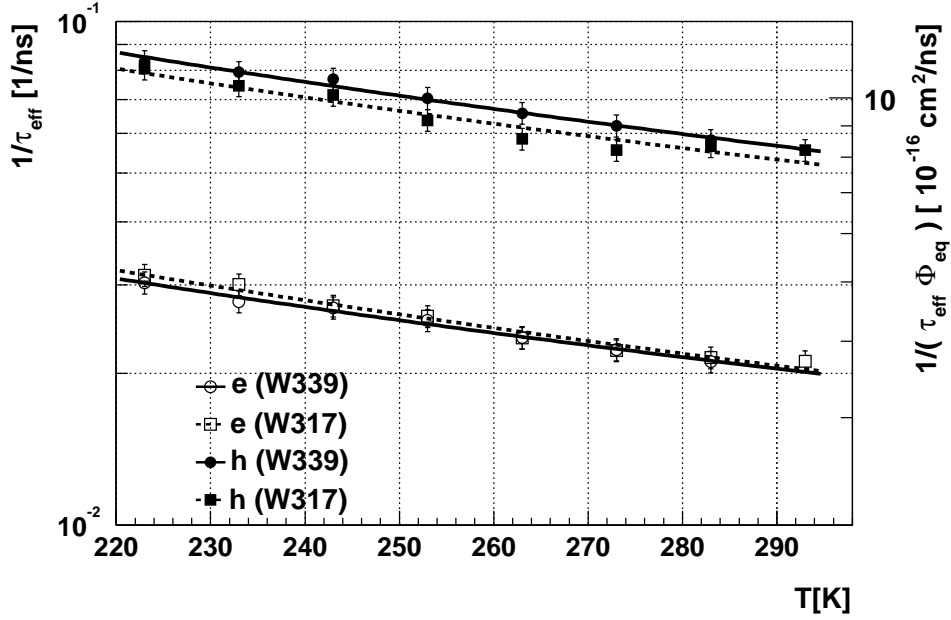


Fig. 5. Temperature dependence of the effective trapping probability for the W317 and W339 samples after the annealing procedure.

After the last annealing step, temperature scans of both diodes were performed. The temperature scaling parameter $\kappa_{e,h}$ (Table 5) of the effective trapping probability was found to be comparable with its value in the minimum of V_{FD} (Table 3) for holes, while for electrons its value increased nearly by a factor of two. As a consequence, the observed β_e decrease in fact turns into an increase at temperatures lower than -40°C.

Table 5

Temperature scaling parameter $\kappa_{e,h}$ as obtained from the fit of Eq. 9 to temperature dependence of the effective trapping probability for diodes W339 and W317 at the end of annealing.

	κ_e	κ_h
W339	-1.55 ± 0.24	-1.50 ± 0.24
W317	-1.58 ± 0.20	-1.50 ± 0.20

4 Conclusions

Several sets of diodes of different resistivities and oxygen content were irradiated with neutrons, pions and protons up to $\Phi_{\text{eq}} = 2.4 \times 10^{14} \text{ cm}^{-2}$. TCT measurements were performed as the irradiated diodes annealed to the minimum in V_{FD} at room temperature. Using the charge correction method the electron and hole effective trapping probabilities were determined for all diodes in the temperature range between 223 K and 293K.

The effective trapping probability was found to scale linearly with fluence and not to depend on oxygenation level and resistivity. Holes were observed to have higher trapping probability than electrons. Charge trapping is seen not to scale according to the NIEL hypothesis since charged hadrons induce 30-40 % more trapping than neutrons at the same NIEL equivalent fluence.

For both electrons and holes the effective trapping probability decreases with temperature by 20-30 % over the investigated -50 to $+20^\circ\text{C}$ temperature range. A power scaling law, universal in terms of particle type, was found to parameterize the data well.

Distinct annealing behavior of effective trapping probability for electrons and holes was observed. The electron effective trapping probability decreases by $\sim 35\%$ while the hole effective trapping probability increases by $\sim 30\%$. Time constants for these changes are of the order of 10 hours at 60°C .

5 Acknowledgments

The authors would like to thank B. Dezillie and Z. Li for providing the BNL samples and to the ROSE collaboration, especially M. Moll, for the STM samples. Special thanks goes to M. Glaser for his assistance with pion and proton irradiations.

References

- [1] ATLAS Collaboration: *Inner Detector Technical Design report Vol I & II*, CERN/LHCC/97-16,17, 1997.
- [2] V. Cindro et al., Nucl. Instr. and Meth. A439 (2000) 337.
- [3] RD48 Collaboration: G.Lindström et al.: *Radiation Hard Silicon Detectors - Developments by the RD48 (ROSE) Collaboration*, presented at 4th STD Hiroshima Conference, Hiroshima, Japan, March 23-25, 2000, ROSE/TN/2000-03, accepted for publication in Nucl. Instr. and Meth. A.
- [4] H.W. Kraner et al., Nucl. Instr. and Meth. A 326 (1993) 350.
- [5] S. Martí i García et al.: *A model of charge collection for irradiated p^+n detectors*, presented at 9th International Workshop on Vertex Detectors, Sleeping Bear Dunes National Lakeshore, Michigan, USA, September 10-15 2000, submitted for publication in Nucl. Instr. and Meth. A.
- [6] G. Kramberger et al.: *Determination of effective trapping time of electrons and holes in irradiated silicon*, presented at 3rd International Conference on Radiation Effects in Semiconductor Materials, Detectors and Devices, Firenze, June 2000, (ATL-INDET-2000-017), submitted for publication in Nucl. Instr. and Meth. A.
- [7] T.J. Brodbeck et al., Nucl. Instr. and Meth. A455 (2000) 645.
- [8] D. Žontar et al., Nucl. Instr. and Meth. A426 (1999) 51.
- [9] E.S. Krištof: *Characterization of Neutron Flux in the Exposure Channel F19 of the TRIGA Mark II Reactor in Ljubljana*, Proceedings of Nuclear Energy in Central Europe '98, Terme Čatež, Slovenia, September 7-10, 1998, p. 43.
- [10] M. Moll et al., Nucl. Instr. and Meth. A426 (1999) 87.
- [11] V. Cindro et al., Nucl. Instr. and Meth. A450 (2000) 290.
- [12] E. Fretwurst et al.: *Relation between microscopic defects and macroscopic changes in silicon detector properties after hadron irradiation*, Report given at 1st International Workshop on Defect Engineering of Advanced Semiconductor Devices Santorini, Greece, April 21-22, 1999.
- [13] A. Ruzin, Nucl. Instr. and Meth. A447 (2000) 116.
- [14] V.N. Abakumov et al., Sov. Phys. Semicond., 12, 1 (1978).
- [15] A. Hall 'en et al., J. Appl. Phys. 79 (1996) 3906.
- [16] G. Lutz, Nucl. Instr. and Meth. A377 (1996) 234.